



A Review on Nanomaterial as Photocatalysts for Degradation of Organic Pollutants

Solomon S. Durodola¹ · Olaniran K. Akeremale² · Odunayo T. Ore¹ · Ajibola A. Bayode³ · Hamza Badamasi⁴ · Johnson Adedeji Olusola^{5,6}

Received: 11 May 2023 / Accepted: 29 June 2023 / Published online: 11 July 2023
© The Author(s), under exclusive licence to Springer Science+Business Media, LLC, part of Springer Nature 2023

Abstract

Eliminating hazardous organic contaminants from water is a major concern today. Nanomaterials with their textural features, large surface area, electrical conductivity, and magnetic properties make them efficient for the removal and photocatalytic degradation of organic pollutants. The reaction mechanisms of the photocatalytic oxidation of common organic pollutants were critically examined. A detailed review of articles published on photocatalytic degradation of hydrocarbons, pesticides, and dyes was presented therein. This review seeks to bridge information gaps on the reported nanomaterial as photocatalysts for the degradation of organic pollutants under sub-headings, nanomaterials, organic pollutants, degradation of organic pollutants, and mechanisms of photocatalytic activities.

Keywords Photocatalytic degradation · Organic pollutants · Nanomaterials

Introduction

Water is an essential resource for life on earth; it is a known fact that fresh water is an important necessity for our health. Recent population growth and globalization have resulted in a rapid spread of industries and, as a result, environmental pollution (Bayode et al. 2020, 2021). In recent times, much attention has been shifted to the release of toxic organic pollutants such as synthetic dyes, pharmaceuticals, steroid estrogens, pesticides, etc. into the water bodies. Synthetic dyes are among well-known occurring organic pollutants, it has been reported that about 280,000 tons of dyes are discharged in industrial effluents annually (Jin et al. 2007;

Kubiak et al. 2019; Ramzan et al. 2019). A report by Adeel and his colleagues (2018) revealed that the world's human population of about 7 billion discharges approximately 30,000 kg/yr of natural steroid estrogen and an additional 700 kg/yr of synthetic estrogens solely from the practice of birth control using pills. The introduction of these pollutants into the water bodies can be direct through the disposal of untreated industrial wastes or indirectly through anthropogenic activities, farm run-offs, and wastewater treatment plants.

These contaminants are detrimental to aquatic ecosystem quality and human health, impairing recreational activities and other uses of water (Wang and Yang 2016). Some of

✉ Solomon S. Durodola
solomonsun77@gmail.com

Olaniran K. Akeremale
okakeremale.ste@buk.edu.ng

Odunayo T. Ore
oreodunayo@yahoo.com

Ajibola A. Bayode
bayodea@run.edu.ng

Hamza Badamasi
hamza.badamasi@fud.edu.ng

Johnson Adedeji Olusola
johnsonolusola06@gmail.com

¹ Department of Chemistry, Obafemi Awolowo University, 220005 Ile-Ife, Nigeria

² Department of Science and Technology Education, Bayero University, 3011 Kano, Nigeria

³ Department of Chemical Sciences, Faculty of Natural Sciences, Redeemer's University, P.M.B. 230, Ede 232101, Nigeria

⁴ Department of Chemistry, Federal University Dutse, Dutse, Jigawa State, Nigeria

⁵ Department of Geography and Planning Science, Ekiti State University, Ado Ekiti, Ekiti State, Nigeria

⁶ Institute of Ecology and Environmental Studies, Obafemi Awolowo University, Ile-Ife 220005, Nigeria

these organic pollutants are classified as persistent organic pollutants (POPs) because they bio-accumulate and are not degradable when they enter water bodies. These organic pollutants can easily travel from the point of contamination to a pristine area or where they have never been produced (Krithiga et al. 2022).

The treatment of wastewater has recently been the subject of numerous scientific investigations. The removal of multi-component contaminants from water resources requires the utilization of efficient water treatment techniques. The wide usage of biological and physicochemical treatment processes in the industry is due to the simplicity of design as well as the enhanced remediation capacity associated with the techniques (Crini and Lichtfouse 2019). Nevertheless, the higher energy consumption associated with these conventional water treatment technologies has been a major impediment in the industry (Maktabifard et al. 2018). Finding a single treatment method that completely covers the efficient removal of all varieties of organic pollutants has become challenging due to the complexity and variety of organic chemicals used. This led to the development of alternative treatment technologies that will ensure the removal of recalcitrant organic pollutants. Some of these advanced treatment techniques comprise UV-illuminated processes, membrane-based processes, and advanced oxidation processes (Abdel-Fatah 2018; Boukhessaim et al. 2022; Gaur et al. 2022). The use of non-destructive physical techniques including flocculation, reverse osmosis, and adsorption on activated charcoal results in secondary pollution because the contaminants are only transferred to new media, hence, there is a need for an effective environmentally benign method for the removal of these pollutants. The main advantage offered by advanced oxidation processes is that it ensures the effective degradation of organic pollutants via the generation of highly reactive hydroxyl radical, as opposed to conventional treatment processes that only ensures the physical transformation of pollutants without necessarily degrading them (Cheng et al. 2016; Krishnan et al. 2017). Among advanced oxidation processes, photocatalytic degradation has proven to be a quick, cost-effective, and environmentally benign method of removing persistent contaminants from water (Khan and Pathak 2020; Samuel et al. 2023).

Several recent studies have described the photocatalytic degradation of organic pollutants using different photocatalysts (Mei et al. 2022; Rostami et al. 2022; Silvestri et al. 2022; Subhiksha et al. 2022; Tang et al. 2022; Wang et al. 2022; Kanakaraju and Chandrasekaran 2023; Pattnaik et al. 2023). However, these studies have been singularly focused on one particular kind of photocatalyst such as metal-based photocatalysts or natural minerals. The present review was designed to focus on the use of nanomaterials as photocatalysts in the degradation of organic pollutants. Here, we described metal-based nanomaterials, carbon-based

nanomaterials, and semi-conductor nanomaterials. In addition, the application of these nanomaterials in the removal of hydrocarbons, pesticides, and dyes was elucidated. Finally, the mechanisms by which photocatalysis occurs were illustrated.

Nanomaterials

Nanomaterials are defined as materials with a size or one of their dimensions that falls within the range of 1 to 100 nm (Laurent et al. 2010; Naseem and Durrani 2021). The unique properties of nanomaterials when compared to their bulk counterparts are significantly different, and their size-dependent effects become more noticeable at the nanoscale level. Surprisingly, by changing the shape and size at the nanoscale level, nanomaterials produce a distinct character with new features and powers (Kolahalam et al. 2019). Nanomaterials occur in different shapes like nanorods, nanosheets, spherical, oval, cubic, cluster, flower, triangular, needle-like, branched, etc. as illustrated in Fig. 1. Based on their form, size, characteristics, and constituents, nanomaterials also exist in different forms. These include polymeric nanomaterials, lipid-based nanomaterials, semiconductor nanomaterials, metal nanoparticles, and carbon-based nanomaterials.

Metal-based Nanomaterials

Metals of trivalent and divalent ions are used as the building blocks for the creation of metal oxide nanoparticles (MONPs). They can be prepared using different techniques such as chemical and photochemical, due to their excellent electrical, optical, magnetic, and catalytic properties MONPs are useful in many fields like photocatalysis (Khalafi et al. 2019), catalysis (Jalpa et al. 2019), sensors, and heavy metal removal (George et al. 2018). Metal oxide nanoparticles (NPs) have attracted a lot of attention in many fields of science like chemistry, physics, and material sciences (Panji et al. 2016). For instance, Zinc oxide has good photocatalytic activity because of its unique properties like large surface area, super oxidative capability, high electrochemical stability, and low toxicity enable it to have a good capacity for the adsorption of small molecules. According to Naseem and Durrani (2021), TiO_2 is the most exceptional photocatalyst, it has low selectivity, making it ideal for degrading a variety of pollutants like polycyclic aromatic hydrocarbons (Guo et al. 2015), chlorinated organic compounds (Ohsaka et al. 2008), dyes (Lee et al. 2008), phenols (Nguyen et al. 2016), Macro and micron size plastics (Nabi et al. 2021), Cyanide (Chiang et al. 2002), Nitrophenols (Augugliaro et al. 1991), Chlorpyrifos, Cypermethrin, and Chlorothalonil (Affam and Chaudhuri 2013).

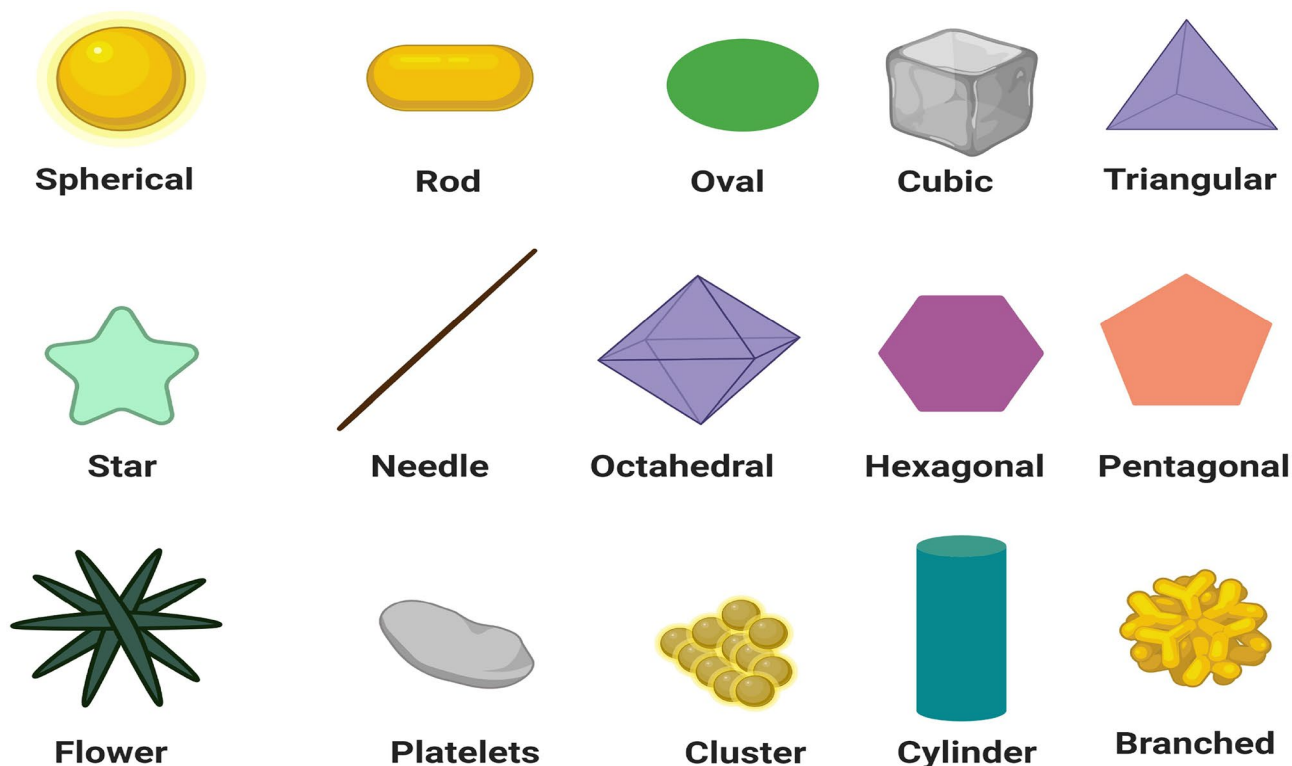


Fig. 1 Different shapes of nanoparticles. (Adapted from Hamida et al. 2020)

Carbon-based Nanomaterials

Carbon-based nanomaterials have recently attracted significant attention due to their outstanding physicochemical features like large surface area, excellent acid stability, and thermal resistance that make them viable candidates for a variety of many applications (Liu et al., 2022; Son et al., 2021). Carbon-based nanomaterials are classified according to their geometrical structure. Carbon nanostructures include particles that might be tube-shaped, horn-shaped, spherical, or ellipsoidal. Nanoparticles having the shape of tubes are called carbon nanotubes; horn-shaped particles are nanohorns, and spheres or ellipsoids belong to the fullerene group (Zaytseva & Neumann, 2016). Some of the shapes of carbon-based nanomaterials are shown in Fig. 2.

Carbon nanotubes (CNTs) are of two types i.e. single walled carbon nanotubes (SWCNTs) and multi-walled carbon nanotubes (MWCNTs). They have high strength, favorable electron affinities, and good electrical conductivity (Scida et al., 2011, Zhao et al., 2015). The carbon allotropes known as carbon nanotubes (CNTs) are made of graphite and are in tabular form. The outside diameter of the tubes ranges from 3 to 30 nm and had at least two layers. Electrically, Single-walled carbon nanotubes can be further divided into metallic and semiconducting SWCNTs (s-SWCNTs and m-SWCNTs), whereas multi-walled carbon nanotubes

mostly exhibit metallic behaviour. CNTs have unique and beneficial characteristics that make them suitable for a variety of electronic, biomedical, and other industrial applications. These characteristics include distinctive optical characteristics, high thermal, low cost, high surface area, high mechanical strength, and electrical conductivity (Chavali and Nikolova, 2019).

Semiconductor Nanomaterials

A wide range of various substances are used to create semiconductor nanocrystals (NCs). They are known as II-VI, III-V, or IV-VI semiconductor nanocrystals, depending on the periodic table groups into which these elements are formed. They exhibit both metallic and non-metallic qualities. They also have wide band gaps, modifying them demonstrates varied properties and exhibits large band gaps. They are commonly used in photocatalysis, electronic devices, drug delivery, solar cells, and environmental remediation (Fang et al. 2020; Sahu 2019).

Applications of Nanomaterials

Unique properties of nanoparticles like mechanical strength, large surface area, optically active, electronically active, high thermal conductivity, and chemically reactive make them

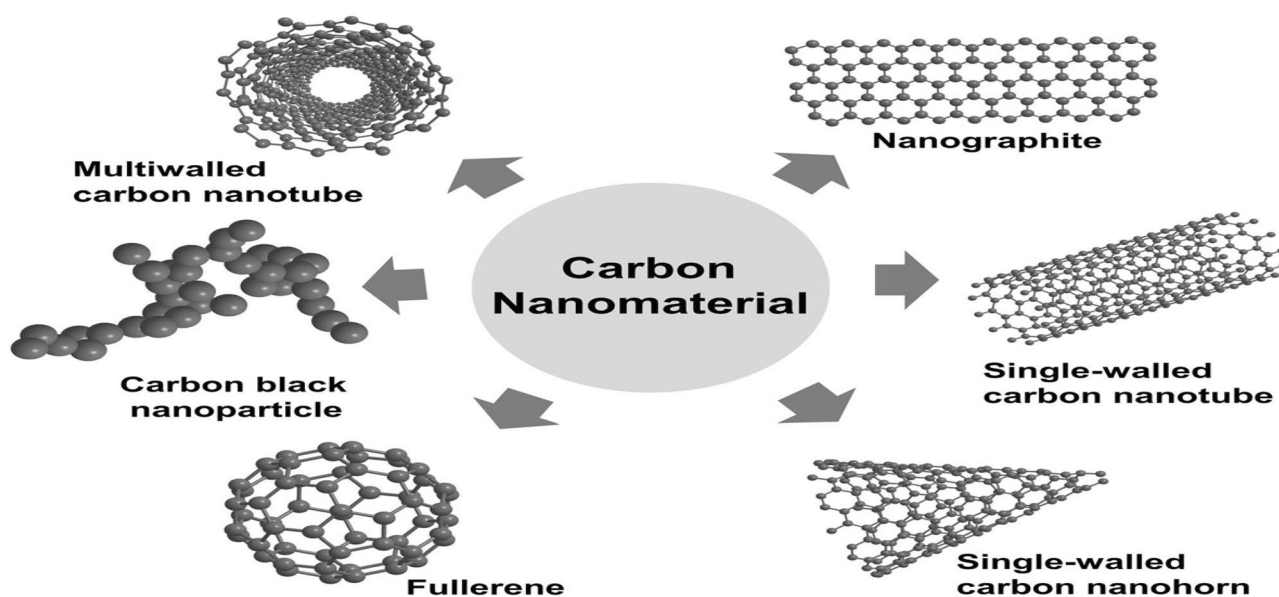


Fig. 2 Different shapes of carbon based nanomaterials. (Adapted from Yuan et al. 2019)

suitable for various applications. Nanomaterials have been used in the development of nanodevices that are found useful in pharmaceutical and biomedical applications (Loureiro et al. 2016; Martis et al. 2012; Nikalje 2015). Iron oxide particles such as magnetite (Fe_3O_4) or its oxidized form haematite (Fe_2O_3) are the most useful for biomedical applications (Ali et al. 2016). They are also used in wastewater treatment, due to their high surface-to-mass ratio, natural nanoparticles (NPs) are crucial in the solid/water partitioning of pollutants as they can either be absorbed onto their surface, coprecipitated during the synthesis of natural NPs, or trapped by NPs that had contaminants adsorb to their surface. (Khan et al. 2019). They are used as sensors, biosensors, and in the modification of electrodes to enhance their performance capability. NPs are found useful in energy storage devices, and also applicable in the form of electrodes (Li et al. 2019), however the importance of nanomaterials in the removal of organic contaminants cannot be overemphasized (Veisi et al. 2019).

Organic Pollutants

Organic pollutants are toxic synthetic chemical compounds that can persist in the environment over a long period of time. When their levels exceed the permissible limits, they become poisonous molecular compounds that can affect humans and cause many diseases. The main sources of these organic compounds are industrial items such as petroleum hydrocarbons, detergents, plastics, organic solvents, dyes, and insecticides. Some of these pollutants can resist degradation and bio-accumulate and remains for decades, they are

classified as persistent organic pollutants (POPs). The salient features of POPs include the followings.

1. Persistence; POPs are not easily degradable either by chemical, physical, or biological degradation. They can retain in the soil, water, and air for decades.
2. Bioaccumulation; they build up inside the body to a point where they could be dangerous to both the environment and human health.
3. The ability to travel vast distances; POPs can travel through environmental media to far locations where they have never been utilized or produced, including the Arctic regions.
4. POPs are very hazardous and endanger both human and environmental health (Alharbi et al. 2018). It has been reported that some health-related issues like reproductive defects, preterm and immune toxicity are associated with exposure to organochlorine pesticides (Dalvie et al. 2004; Longnecker et al. 2001; Oyekunle et al. 2021), diseases like cancer, obesity e.t.c is found to associate with Polychlorinated biphenyl (Penell et al. 2014; Roos et al. 2013), also many PAHs have been reported to possess carcinogenic and genotoxic properties (Oyekunle et al. 2019; Rengarajan et al. 2015).

Hydrocarbons

Hydrocarbon contamination in the environment is a very serious issue whether it comes from petroleum, insecticides, or other hazardous organic materials. Being poisonous to all forms of life, petroleum hydrocarbons raise

serious concerns about environmental pollution. Polycyclic aromatic hydrocarbons are organic pollutants that are typically colorless, white, or light-yellow solid substances composed of two or more fusions of carbon and hydrogen aromatic rings (Abdel-Shafy and Mansour 2016; Suman et al. 2016). The highest water solubility is seen in low molecular weight PAHs compounds like naphthalene, acenaphthene, and acenaphthylene while solubility declines with increasing molecular mass. They are categorized as semi-volatile chemicals because they have a low vapour pressure. However, as molecular weight increases, so do their boiling and melting points. The International Agency for Research on Cancer (IARC) has identified sixteen (16) PAHs that pose serious risks to human health because of their propensity to cause cancer and mutagenesis. These are Acenaphthene, Benzo(k)fluoranthene, Naphthalene, Benzo(a)anthracene, Chrysene, Benzo(a)pyrene, Acenaphthylene, Fluoranthene, Dibenzo(a,h)anthracene, Benzo(b)fluoranthene, Benzo(ghi)perylene, Phenanthrene, Benzo(j)fluoranthene, Indeno(1,2,3,d)pyrene, Anthracene, and Pyrene (European Union 2005; Keith and Telliard 1979; Yun et al. 2017; Zhang et al. 2020).

Pesticides

A pesticide is any substance that is used to eradicate, deter, or restrain specific plant or animal life forms that are regarded as pests. Most of the chemicals used in the production of pesticides belong to the family of carbamates, organochlorides, pyrethroids, organophosphates, and other substances (Intisar et al. 2022). Among these classes of pesticides, organochlorine is the most dangerous with deleterious effects on human health (Rani et al. 2017). An organochlorine compound is an organic compound that has at least one chlorine atom covalently attached to it as the main functional component. They have a wide range of applications due to their wide structural variety and divergent chemical properties, OCPs are chlorinated hydrocarbons that were extensively used in agriculture and mosquito control from the 1940s to the 1960s. Examples of compounds in this group include DDT, DDE, methoxychlor, Lindane, Endosulfan, Chlordane, Diclof-methyl, Dieldrin, toxaphene, mirex, Aldrin, DDD, and Benzene hexachloride. Up until 1980, the use of these organochlorine pesticides (OCPs) was extremely successful; however, suggestions for controlled usage of OCPs were made due to the serious health risks they posed, including the potential for cancer, endocrine disruption, immune system disorders, reproductive issues, and other chronic diseases as a result of their persistence or strong resistance in ambient environmental conditions. (Augustijn-Beckers et al. 1994; Kumar et al. 2013; Syafrudin et al. 2021).

Dyes

Dyes are compounds that give color to a surface when applied through a process that modifies if only temporarily, the crystal structure of the colored substances (Bafana et al. 2011). They are substances, both natural and artificial that add colour to the world and enhance its beauty.

A group of organic chemicals known as textile dyes are frequently regarded as contaminants and are mostly released into wastewater as a result of chemical textile finishing processes. According to estimates, over 10,000 different types of dyes and pigments are utilized in industry, and more than 7 million tons of synthetic dyes are produced annually around the world (Ogugbue and Sawidis 2011; Robinson et al. 2001). Azo dyes are the most used dyes and account for more than 60% of total dyes (Gürses et al. 2016; Shah 2014) and approximately 70% of all the dyes used in the industry are azo dyes (Lipskikh et al. 2018; Berradi et al. 2019). Azo compounds have been used in a variety of scientific and industrial fields, including color waxes, oils, gasoline, solvents, polishes, paper, varnish, food, leather, plastics, cosmetic medicine, and automobiles (Al-Khuzai and Al-Majidi 2020; Dixit et al. 2007; Guerra et al. 2018; Patel and Dixit 2014).




Additionally, they are employed as antibacterial, anti-diabetic, and anti-tumor agents (Adu et al. 2020; Rabbani et al. 2020).

Photocatalytic Degradation of Organic Pollutants Using Metal Oxide Nanomaterials

Photocatalysis is the process that takes place when a light source interacts with the semiconductor components that make up the photocatalyst on its surface (Adeola et al. 2023; Alegbeleye et al. 2022; Ore et al. 2023). However, this process depends on in-situ photogenerated hydroxyl radicals (OH^-), superoxide radicals (O_2^-), and positively charged holes (h^+) which completely degrade organic contaminants. Oxidation from photogenerated holes and reduction of photogenerated electrons are the two simultaneous processes that take place during this process (Adeola et al. 2022). Consequently, the process of removing impurities by photocatalysis is effective, ecologically benign, inexpensive, and simple (Zhang et al. 2018). Jiang et al. (2015) synthesized an aggregate silver oxide nanoparticle that demonstrated excellent photocatalytic performance in both artificial and natural light. According to the result, methyl orange decomposed under near-infrared light in 40 min and under sunlight, artificial ultraviolet, and visible light in 120 s. Fe_3O_4 mesoporous carbon shell was used by Angamuthu et al. (2017) to develop nanomaterial that was used to degrade the dye methylene blue, with this

artificial nanomaterial, methylene blue dye was degraded with excellent catalytic activity. In 2019, Kubiak and his colleagues published a paper on the synthesis of extremely crystalline photocatalysts based on TiO₂ and ZnO for the oxidation of organic contaminants. The created TiO₂-ZnO binary oxide systems exhibit remarkable photodegradation efficiency of organic contaminants of 90%. In their 2018 study, Harun et al. (2018) examined the effectiveness of photocatalytic degradation in the absence and presence of a photocatalyst as well as the impact of a light source for the decolorization of Congo red dye under solar and UV light, TiO₂ was the catalyst utilized. Sunlight and artificial UV light both have a 30 min degradation rate of the dye of up to 64.72% and 66.99%, respectively. Photocatalytic oxidation of phenol was studied by Hayat et al. (2011), it was reported that the Photocatalytic degradation efficiency of phenol was 97% using nano NiO and UV laser irradiation was accomplished in a short amount of time as compared with conventional setups like lamps. Jassal and his coworkers (2015) reported photocatalytic degradation of Eriochrome Black T (EBT) and Malachite MG Green with degradation efficiency of 94.15% and 76.13% for MG and EBT respectively using nanocubes. Ullah and Dutta (2008) used Mn doped ZnO NPs for photodegradation, and their photocatalytic effectiveness was determined by the degradation of aniline and MB dyes under visible light from a tungsten lamp. It was reported that ZnO-Mn²⁺ NPs can be employed as a better photocatalyst than undoped ZnO since Mn doped ZnO demonstrated a 50% higher degradation rate than undoped ZnO. The potential of cobalt and cobalt oxide nanoparticles as nanocatalysts for the degradation of murexide and EBT dye in wastewater in the presence of sunshine was investigated by Adekunle et al. (2020). The highest degradation efficiency was reported for chemically synthesized Co-nanoparticles (43.6%) toward murexide dye at 25 mg loading and 40 min exposure time, while the highest degradation efficiency for microwave-synthesized Co₃O₄ nanoparticles (39.4%) was reported for EBT at 10 mg loading and 40 min sunlight exposure time. Adekunle and his colleagues worked on a study comparing the photocatalytic degradation of dyes in wastewater utilizing solar-enhanced iron oxide (Fe₂O₃) nanocatalysts made by chemical and microwave processes. According to the research, microwave-produced Fe₂O₃ nanoparticles had the highest degradation rates for the dyes Murexide (98%) and EBT (96%) at a 25 mg loading and 40 min exposure, whereas chemically produced Fe₂O₃ nanoparticles had the highest degradation rates for the dye Murexide (15.2%) at a 5 mg loading and 30 min sunlight exposure. With 15 mg of catalyst loading and 40 min of exposure, the chemically produced Fe₂O₃ nanoparticles in EBT degraded at a rate of 21.4%. (Adekunle et al. 2021).

The mechanism of the degradation of EBT and murexide is illustrated in Eqs. (1)–(4) below.



Photocatalytic Degradation of Organic Pollutants Using Carbon-based Nanostructures

Carbon-based nanostructures could be viewed as an ideal candidate for enhancing the photocatalytic effectiveness of nanoparticles by facilitating the transferring of photo-generated electrons and reducing charge recombination.

One report by Nguyen et al. (2018), utilized graphene oxide (GO) as a support for the deposition of ZnO NPs through a simple hydrothermal process, in which GO prevent ZnO particle from aggregation as well as the efficient separation of photo-generated electrons and holes (e⁻ and h⁺) on the surface of the ZnO. The nanocomposite was successfully used for the degradation of methyl orange (MO) during which more than 95% of MO was decomposed at optimal conditions.

In a work reported by Atchudan et al. (2017) that involves the degradation of MO and MB using TiO₂-GO nanocomposite, a maximal degradation efficiency of 84% and 100% were obtained for MO and MB respectively by using a two-step sol-gel deposition technique. Durmus et al. (2019) synthesized a GO/ZnO nanocomposite catalyst and was successfully used as a photocatalyst to degrade the basic fuchsin (BF) dye. The degradation of BF dye, a model compound in an aqueous media, was found to be more effectively photocatalyzed by the nanocomposite structure because it decreased the band gap of ZnO nanoparticles. Khataee and his co-workers in their work on photocatalytic degradation of organic dyes illustrate how photogenerated electron-hole pairs by the synthesized nanoparticle facilitate the degradation of organic pollutants. It was observed that when TiO₂ is irradiated with light, an electron excites out of its energy level, leaving a hole in the valence band and electrons are promoted from the valence band to the TiO₂ conduction band, resulting in electron-hole pairs (Khataee and Kasiri 2010) as shown in Fig. 3 below.

Jo et al. (2017) worked on the photocatalytic degradation of oxytetracycline and Congo red using Cobalt-titanium

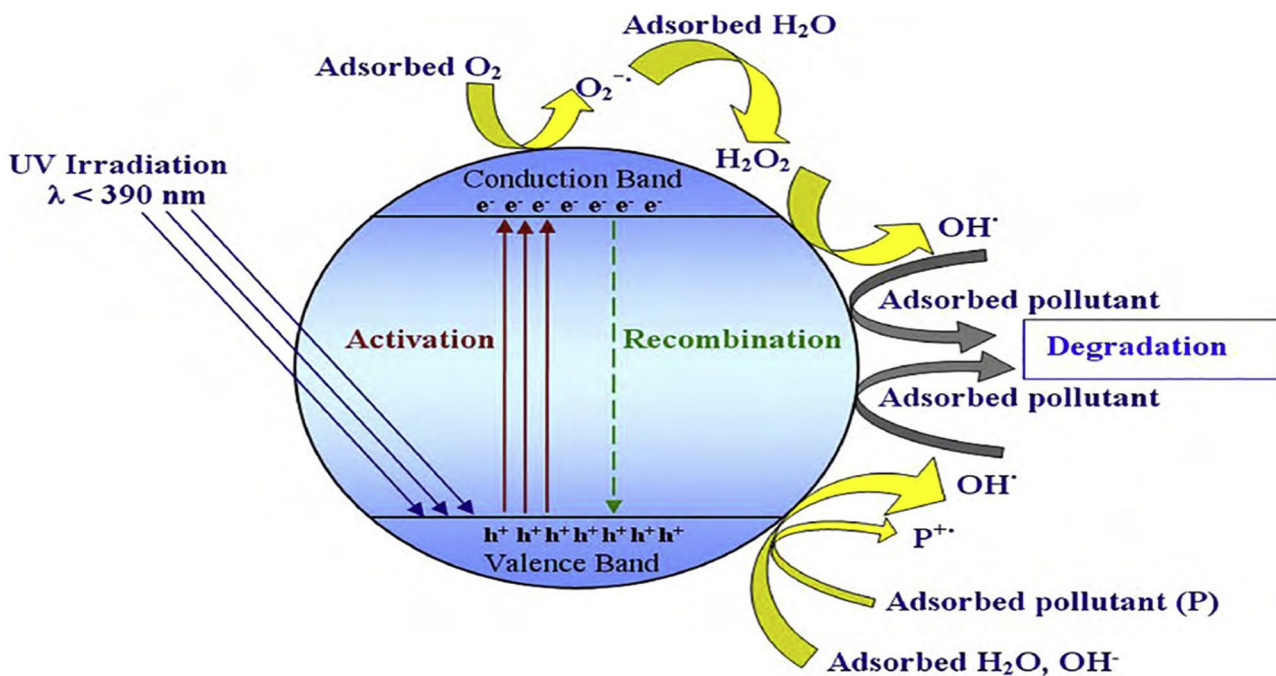


Fig. 3 General mechanism of the photocatalysis on TiO₂ nanomaterial. [Reprinted from Khataee and Kasiri 2010]

mixed metal oxides. It was discovered that the photocatalytic oxidative destruction of oxytetracycline and Congo red was greatly improved by heterojunction formation between a low concentration of discrete Co₃O₄ nanoparticles and anatase titania, which was further enhanced by the addition of trace Graphene oxide as shown in Fig. 4.

A list of different percentages of degradation of some organic pollutants by some nanomaterials as reported in some literature is given in Table 1 below.

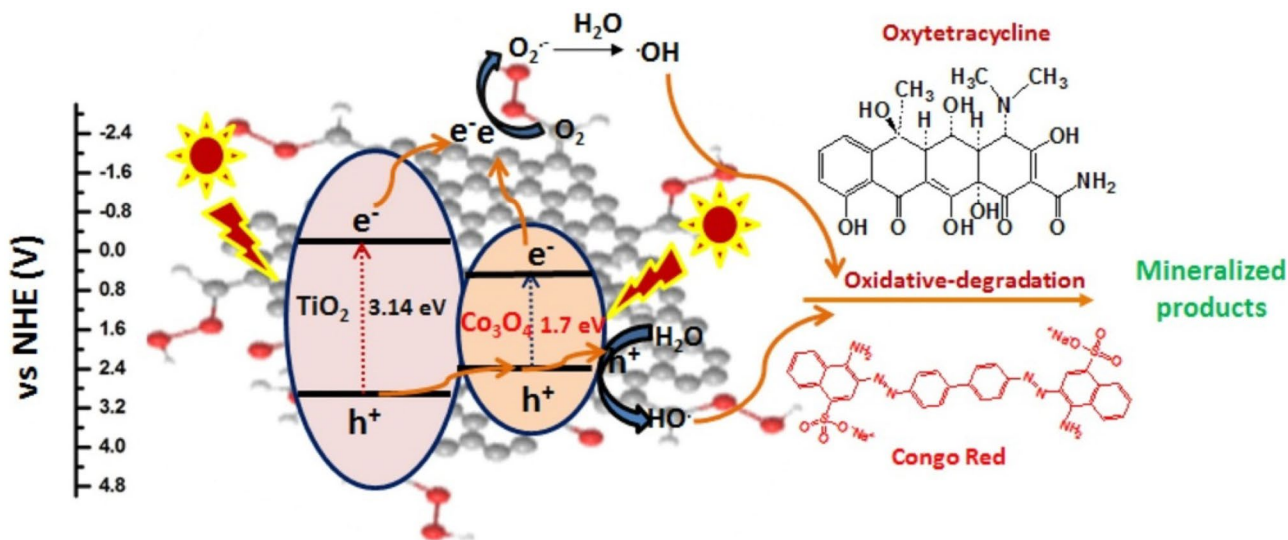


Fig. 4 Proposed mechanism for the photocatalytic degradation of organic pollutants by Co₃O₄/TiO₂/GO nanocomposite. (Reprinted from Jo et al. 2017)

Table 1 Percentage degradation of some organic pollutants using nanomaterials

Organic pollutant	Catalyst	% degradation	References
EBT	Bi ₂ WO ₆ NPs	74	Lai et al. (2019)
EBT	KZnHCF	76.13	Jassal et al. (2015)
MG	KZnHCF	94.15	Jassal et al. (2015)
EBT	CO ₃ O ₄ NPs	39.4	Adekunle et al. (2020)
Paracetamol	TiO ₂ -G	88	Vaiano et al. (2018)
Malathion	Zn ²⁺ -doped TiO ₂	98	Nasseri et al. (2018)
EBT	SnO ₂ NPs	94	Srivastava and Mukhopadhyay (2014)
EBT	ZnFe ₂ O ₄ NPs	92	Ikramullah et al. (2020)
Metronidazole	BiVO ₄ /N-rGO	95	Appavu et al. (2018)
EBT	ZnO	90	Kaur and Singhal (2015)
EBT	BiFeO ₃ NPs	64.6	Khan et al. (2020)
Congo Red	BiVO ₄ /N-rGO	95	Appavu et al. (2018)
EBT	Fe ₂ O ₃	96	Adekunle et al. (2021)
Murexide	Fe ₂ O ₃	98	Adekunle et al. (2021)
Chloramphenicol	BiVO ₄ /N-rGO	93	Appavu et al. (2018)
Murexide	TiO ₂ NPs - AC	98	Davoodi et al. (2014)
Methylene blue	BiVO ₄ /N-rGO	98	Appavu et al. (2018)
Murexide	ZnO NPs	45.1	Alkhateeb et al. (2007)
Murexide	TiO ₂ NPs	60.1	Alkhateeb et al. (2007)
Ciprofloxacin	ZnO/ZnAl ₂ O ₄ /rGO	90.6	Ni et al. (2018)
Murexide	BiFeO ₃ NPs	83.4	Khan et al. (2020)
Phenol	Fe-Fe ₃ O ₄ -GO	87	Le et al. (2018)
Phenol	Fe ₃ O ₄ -GO	75	Le et al. (2018)
Endosulfan	TiO ₂	99	Sivagami et al. (2016)
Chlorpyrifos	TiO ₂	94	Sivagami et al. (2016)
Amido black dye	Co/TiO ₂	90	Ali et al. (2018)
Azo dye	CdS	95	Senasu and Nanan (2017)
Methylene blue	NiO-ZnO	97	Rogozea et al. (2017)
Methylene blue	AKB	94	Zhou et al. (2018)
Rhodamine B	BiOI/N-doped rGO	83	Lu et al. (2018)
Remazol yellow RR dye	α-Fe ₂ O ₃	77	Bhuiyan et al. (2020)
Acid blue 74 dye	Ag-Ag ₂ O-ZnO/GO	90	Umukoro et al. (2016)


Mechanism of Photocatalytic Activity

A chemical reaction known as photocatalysis is initiated by light and takes place when the compound comes into contact with photons with high enough energies to trigger free radical processes. The mechanism of organic pollutant photo-oxidation can take place in two ways, direct or indirect.

(a) Direct degradation mechanism

This type of photocatalytic degradation takes place under visible light because of the ease of absorption of some visible light. This mechanism involves the excitation from the ground state of the organic pollutant to the triplet excited state (organic pollutant) under visible light photons (> 400 nm). A further transformation of the excited state

organic pollutant species into a partially oxidized radical cation (Dye⁺) is accomplished by injecting an electron into the conduction band of the nanoparticle. The system-dissolved oxygen and these trapped electrons combine to produce superoxide radical anions (O₂⁻), which in turn lead to the creation of hydroxyl radicals (OH⁻). The oxidation of organic molecules is mostly caused by these OH⁻ radicals as represented by Eqs. (5) and (6) below.



The entire process can be summarized using the Fig. 5 below.

(b) Indirect dye degradation mechanism.


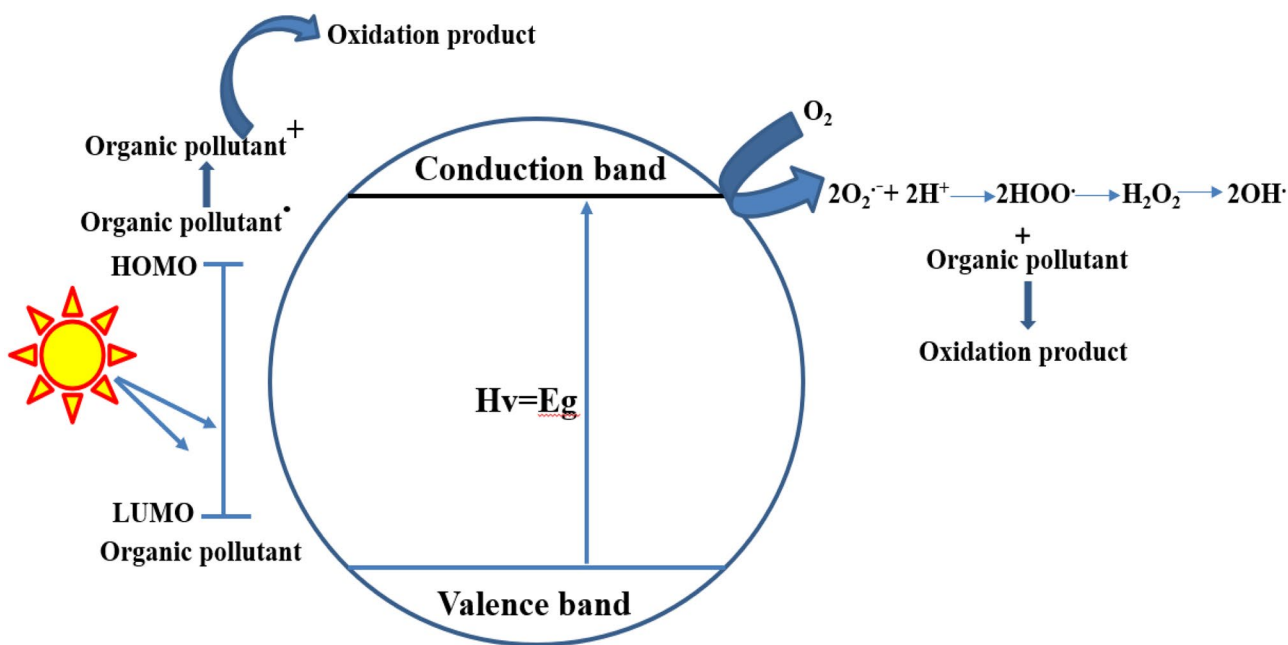


Fig. 5 Pictorial representation of direct organic pollutant degradation process. (Adapted from Ajmal et al. 2014)

The photocatalytic reaction starts when a photoelectron is promoted from the filled valence band of a semiconductor photocatalyst when it is exposed to radiation. The energy of the absorbed photon ($h\nu$) is equal to or higher than the semiconductor photocatalyst's band gap. A hole ($h\nu_{VB}^+$) is left in the valence band because of excitation, consequently leading to the generation of an electron and hole pair (e^-/h^+) as illustrated in Eq. (7) below.



The water and the photogenerated holes in the valence band subsequently combine to form the hydroxyl radical (Eq. 8).







Adsorbed organic molecules or those that are very near the catalyst surface are attacked non-selectively by the hydroxyl radical that forms on the irradiation semiconductor surface, and this causes them to mineralize to a degree depending on their structure and stability level.

While the photogenerated hole ($h\nu_{VB}^+$) reacts with surface-bound water or OH^- to create the hydroxyl radical, the electron in the conduction (e_{CB}^-) is taken up by the oxygen to create an anionic superoxide radical (O_2^-),

which may participate in further oxidation but also prevents electron-hole recombination, maintaining electron neutrality within the semiconductor molecule.



The hydroperoxyl radical (HO_2^\cdot) that is formed from the superoxide (O_2^-) is protonated to form H_2O_2 , which further dissociates into highly reactive hydroxyl radicals (OH^\cdot).



Both oxidation and reduction processes occur frequently on the surface of the photoexcited semiconductor photocatalyst. The overall process of these reactions can be summarized using Fig. 6 below.

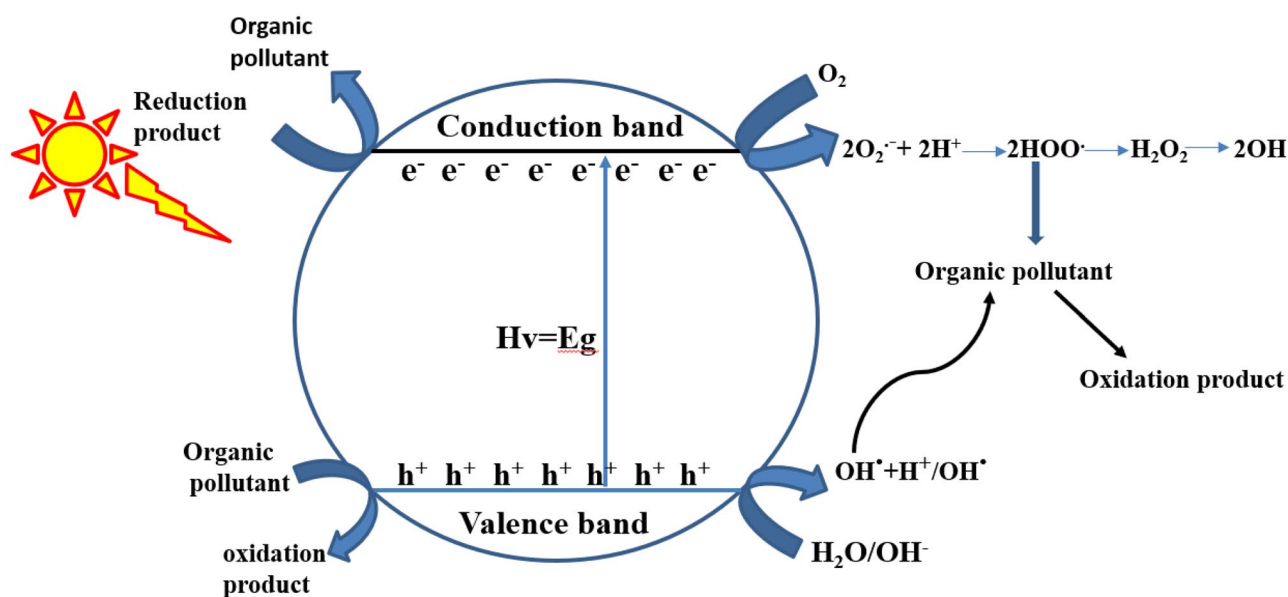


Fig. 6 Pictorial representation of indirect organic pollutant degradation process. (Adapted from Ajmal et al. 2014)

Conclusion

The increase in organic contamination of water bodies through anthropogenic activities is a major concern due to their bioaccumulation and adverse health effects on man and his environment. This paper reviewed studies addressing the photocatalytic degradation of organic pollutants. It was observed that strong oxidizing agents like hydroxyl and related radicals can break down any organic pollutant into smaller degradation products that are either practically innocuous or less toxic. Different organic contaminants like hydrocarbons, steroid estrogens, pharmaceuticals, dyes, pesticides, phenols, etc. can be photo-oxidized by hydroxyl radicals. Filtration, ion exchange, coagulation/flocculation, aerobic degradation, anaerobic degradation, ozonation, and photocatalytic processes are just a few of the techniques that have been utilized to remove organic pollutants from wastewater. As an alternative to physical, chemical, and biological processes, photocatalysis employing nanomaterials showed greater potential than the aforementioned techniques. Furthermore, nanocatalysts quickly oxidize and are cheap, chemically stable, and environmental-friendly. While these photocatalysts have shown relatively high degradation of the studied organic pollutants, it appeared that the efficiency of the process is largely driven by the choice of photocatalysts. The choice of photocatalyst equally depends on the target pollutant. There is significant variation in the ability of different photocatalysts to interact with specific pollutants and initiate essential chemical processes. Understanding the

photocatalytic characteristics of various materials, as well as their interactions with certain pollutants, is therefore critical for achieving optimal degradation efficiencies. It is recommended that further research should be directed into the development of highly efficient photocatalytic materials for the abatement of these recalcitrant organic pollutants. Also, attention should be focused on improving the selectivity of nanomaterials for the removal of these pollutants so that photocatalytic technology can gain ground in industrial applications.

Author Contributions Solomon S. Durodola: Conceptualization, Methodology, Investigation, Writing – original draft, Writing – review & editing. Olaniran K. Akeremale: Writing – original draft, Writing – review & editing. Odunayo T. Ore: Methodology, Investigation, Writing – original draft, Writing – review & editing. Ajibola A. Bayode: Writing – original draft, Writing – review & editing. Hamza Badamasi: Writing – original draft, Writing – review & editing. Johnson Adedeji Olusola: Writing – original draft, Writing – review & editing.

Funding This research received no external funding.

Data Availability and Materials The data generated and/or analyzed will be made available upon reasonable request from the corresponding authors.

Declarations

Ethical Approval Not Applicable.

Competing Interest The authors declare that they have no competing interests.

References

- Abdel-Fatah MA (2018) Nanofiltration systems and applications in wastewater treatment. *Ain Shams Eng J* 9(4):3077–3092
- Alharbi OM, Khattab RA, Ali I (2018) Health and environmental effects of persistent organic pollutants. *J Mol Liq* 263:442–453
- Abdel-Shafy HI, Mansour MS (2016) A review on polycyclic aromatic hydrocarbons: source, environmental impact, effect on human health and remediation. *Egyptian J Petroleum* 25(1):107–123
- Adeel M, Yang YS, Wang YY, Song XM, Ahmad MA, Rogers HJ (2018) Uptake and transformation of steroid estrogens as emerging contaminants influence plant development. *Environ Pollut* 243:1487–1497
- Adekunle AS, Oyekunle JA, Durosinmi LM, Oluwafemi OS, Olayanju DS, Akinola AS, Ajayeoba TA (2020) Potential of cobalt and cobalt oxide nanoparticles as nanocatalyst towards dyes degradation in wastewater. *Nano-Struct Nano-Objects* 21:100405
- Adekunle AS, Oyekunle JA, Durosinmi LM, Saheed O, Ajayeoba TA, Akinyele OF, Oluwafemi OS (2021) Comparative photocatalytic degradation of dyes in wastewater using solar enhanced iron oxide (Fe_2O_3) nanocatalysts prepared by chemical and microwave methods. *Nano-Struct Nano-Objects* 28:100804
- Adeola AO, Abiodun BA, Adenuga DO, Nomngongo PN (2022) Adsorptive and photocatalytic remediation of hazardous organic chemical pollutants in aqueous medium: a review. *J Contam Hydrol* 248:104019
- Adeola AO, Ore OT, Adedipe DT, Nomngongo PN (2023) Green Noncarbon-Based nanomaterials for environmental remediation. In: Policarpo Tonelli FM, Roy A, Murthy A, H.C. (eds) *Green Nanoremediation*. Springer, Cham. https://doi.org/10.1007/978-3-031-30558-0_9
- Adu JK, Amengor CD, Mohammed Ibrahim N, Amaning-Danquah C, Owusu Ansah C, Gbadago DD, Sarpong-Agyapong J (2020) Synthesis and in vitro antimicrobial and anthelmintic evaluation of naphtholic and phenolic azo dyes. *J Trop Med*
- Affam AC, Chaudhuri M (2013) Degradation of pesticides chlorpyrifos, cypermethrin and chlorothalonil in aqueous solution by TiO_2 photocatalysis. *J Environ Manage* 130:160–165
- Ajmal A, Majeed I, Malik RN, Idriss H, Nadeem MA (2014) Principles and mechanisms of photocatalytic dye degradation on TiO_2 based photocatalysts: a comparative overview. *RSC Adv* 4(70):37003–37026
- Alegbeleye O, Daramola OB, Adetunji AT, Ore OT, Ayantunji YJ, Omole RK, ..., Adekoya SO (2022) Efficient removal of antibiotics from water resources is a public health priority: a critical assessment of the efficacy of some remediation strategies for antibiotics in water. *Environ Sci Pollut Res* 29(38):56948–57020
- Al-Khuzai MG, Al-Majidi SM (2020) Synthesis and characterization of new azo compounds linked to 1, 8-naphthalimide as new fluorescent dispersed dyes for cotton fibers. In *Journal of Physics: Conference Series* 1664(1):012065. IOP Publishing
- Alkhatieb A, Ismail J, Hussein F (2007) Solar photolysis and photocatalytic degradation of murexide using titanium dioxide and zinc oxide. *J Arab Univ Basic Appl Sci* 4:70–76
- Ali A, Zafar H, Zia M, ul Haq I, Phull AR, Ali JS, Hussain A (2016) Synthesis, characterization, applications, and challenges of iron oxide nanoparticles. *Nanotechnol Sci Appl* 49–67
- Ali I, Alharbi OM, Allothman ZA, Badjah AY (2018) Kinetics, thermodynamics, and modeling of amido black dye photodegradation in water using Co/TiO_2 nanoparticles. *Photochem Photobiol* 94(5):935–941
- Angamuthu M, Satishkumar G, Landau MV (2017) Precisely controlled encapsulation of Fe_3O_4 nanoparticles in mesoporous carbon nanodisk using iron-based MOF precursor for effective dye removal. *Microporous Mesoporous Mater* 251:58–68
- Appavu B, Thiripuranthagan S, Ranganathan S, Erusappan E, Kannan K (2018) $\text{BiVO}_4/\text{N-rGO}$ nano composites as highly efficient visible active photocatalyst for the degradation of dyes and antibiotics in eco system. *Ecotoxicol Environ Saf* 151:118–126
- Atchudan R, Edison TNJI, Perumal S, Karthikeyan D, Lee YR (2017) Effective photocatalytic degradation of anthropogenic dyes using graphene oxide grafting titanium dioxide nanoparticles under UV-light irradiation. *J Photochem Photobiol A* 333:92–104
- Augugliaro V, Palmisano L, Schiavello M, Sclafani A, Marchese L, Martra G, Miano F (1991) Photocatalytic degradation of nitrophenols in aqueous titanium dioxide dispersion. *Appl Catal* 69(1):323–340
- Augustijn-Beckers PW, Hornsby AG, Wauchope RD (1994) Additional properties reviews of environmental contamination and toxicology. *SCS/ARS/CES Pesticide Properties Datab Environ Decisionmaking II* 137:1–82
- Bafana A, Devi SS, Chakrabarti T (2011) Azo dyes: past, present and the future. *Environ Reviews* 19(NA):350–371
- Bayode AA, Agunbiade FO, Omorogie MO, Moodley R, Bodede O, Unuabonah EI (2020) Clean technology for synchronous sequestration of charged organic micro-pollutant onto microwave-assisted hybrid clay materials. *Environ Sci Pollut Res* 27:9957–9969
- Bayode AA, dos Santos DM, Omorogie MO, Olukanni OD, Moodley R, Bodede O, ..., Unuabonah EI (2021) Carbon-mediated visible-light Fe_2O_3 -graphene oxide catalytic nanocomposites for the removal of steroid estrogens from water. *J Water Process Eng* 40:101865
- Berradi M, Hsissou R, Khudhair M, Assouag M, Cherkaoui O, El Bachiri A, Harfi E, A (2019) Textile finishing dyes and their impact on aquatic environs. *Heliyon* 5(11):e02711
- Bhuiyan MSH, Miah MY, Paul SC, Aka TD, Saha O, Rahaman MM, ..., Ashaduzzaman M (2020) Green synthesis of iron oxide nanoparticle using *Carica papaya* leaf extract: application for photocatalytic degradation of remazol yellow RR dye and antibacterial activity. *Heliyon* 6(8):e04603
- Boulkheissaim S, Gacem A, Khan SH, Amari A, Yadav VK, Harharah HN, ..., Jeon BH (2022) Emerging trends in the remediation of persistent organic pollutants using nanomaterials and related processes: a review. *Nanomaterials* 12(13):2148
- Chavali MS, Nikolova MP (2019) Metal oxide nanoparticles and their applications in nanotechnology. *SN Appl Sci* 1(6):1–30
- Cheng M, Zeng G, Huang D, Lai C, Xu P, Zhang C, Liu Y (2016) Hydroxyl radicals based advanced oxidation processes (AOPs) for remediation of soils contaminated with organic compounds: a review. *Chem Eng J* 284:582–598
- Chiang K, Amal R, Tran T (2002) Photocatalytic degradation of cyanide using titanium dioxide modified with copper oxide. *Adv Environ Res* 6(4):471–485
- Crini G, Lichtfouse E (2019) Advantages and disadvantages of techniques used for wastewater treatment. *Environ Chem Lett* 17:145–155
- Dalvie MA, Myers JE, Thompson ML, Robins TG, Dyer S, Riebow J, ..., Kruger P (2004) The long-term effects of DDT exposure on semen, fertility, and sexual function of malaria vector-control workers in Limpopo Province, South Africa. *Environ Res* 96(1):1–8
- Davoodi S, Marahel F, Ghaedi M, Roosta M, Hekmati Jah A (2014) Tin oxide nanoparticles loaded on activated carbon as adsorbent for removal of Murexide. *Desalination Water Treat* 52(37–39):7282–7292

- Dixit BC, Patel H, Desai DJ (2007) Synthesis and application of new mordant and disperse azo dyes based on 2, 4-dihydroxybenzophenone. *J Serb Chem Soc* 72(2):119–127
- Durmus Z, Kurt BZ, Durmus A (2019) Synthesis and characterization of graphene oxide/zinc oxide (GO/ZnO) nanocomposite and its utilization for photocatalytic degradation of basic fuchsin dye. *ChemistrySelect* 4(1):271–278
- European Union (2005) Commission recommendation 2005/108/EC. *Official J Eur Community Law* 34:43
- Fang J, Zhou Z, Xiao M, Lou Z, Wei Z, Shen G (2020) Recent advances in low-dimensional semiconductor nanomaterials and their applications in high-performance photodetectors. *InfoMat* 2(2):291–317
- Gaur N, Dutta D, Singh A, Dubey R, Kamboj DV (2022) Recent advances in the elimination of persistent organic pollutants by photocatalysis. *Front Environ Sci* 10:2076
- George JM, Antony A, Mathew B (2018) Metal oxide nanoparticles in electrochemical sensing and biosensing: a review. *Microchim Acta* 185(7):1–26
- Guerra E, Llompart M, Garcia-Jares C (2018) Analysis of dyes in cosmetics: challenges and recent developments. *Cosmetics* 5(3):47
- Guo M, Song W, Wang T, Li Y, Wang X, Du X (2015) Phenyl-functionalization of titanium dioxide-nanosheets coating fabricated on a titanium wire for selective solid-phase microextraction of polycyclic aromatic hydrocarbons from environment water samples. *Talanta* 144:998–1006
- Gürses A, Açıkıldız M, Güneş K, Gürses MS (2016) Classification of dye and pigments. *Dyes and pigments*. Springer, Cham, pp 31–45
- Hamida RS, Ali MA, Redhwan A, Bin-Meferij MM (2020) Cyanobacteria—a promising platform in green nanotechnology: a review on nanoparticles fabrication and their prospective applications. *Int J Nanomed* 6033–6066
- Harun NH, Rahman MA, Kamarudin WW, Irwan Z, Muhammad A, Akhir NE F. M., Yaafar MR (2018) Photocatalytic degradation of Congo red dye based on titanium dioxide using solar and UV lamp. *J Fundamental Appl Sci* 10(15):832–846
- Hayat K, Gondal MA, Khaled MM, Ahmed S (2011) Effect of operational key parameters on photocatalytic degradation of phenol using nano nickel oxide synthesized by sol–gel method. *J Mol Catal A: Chem* 336(1–2):64–71
- Ikramullah, Ali N, Ali F, Sheikh ZA, Bilal M, Ahmad I (2020) Photocatalytic performance of zinc ferrite magnetic nanostructures for efficient eriochrome black-T degradation from the aqueous environment under unfiltered sunlight. *Water Air Soil Pollut* 231:1–12
- Intisar A, Ramzan A, Sawaira T, Kareem AT, Hussain N, Din MI, ..., Iqbal HM (2022) Occurrence, toxic effects, and mitigation of pesticides as emerging environmental pollutants using robust nanomaterials—A review. *Chemosphere* 293:133538
- Jalpa AV, Pragnesh ND, Shalini C (2019) The catalytic activity of transition metal oxide nanoparticles on thermal decomposition of ammonium perchlorate. *Def Technol* 15(4):629–635
- Jassal V, Shanker U, Kaith BS, Shankar S (2015) Green synthesis of potassium zinc hexacyanoferrate nanocubes and their potential application in photocatalytic degradation of organic dyes. *RSC Adv* 5(33):26141–26149
- Jiang W, Wang X, Wu Z, Yue X, Yuan S, Lu H, Liang B (2015) Silver oxide as superb and stable photocatalyst under visible and near-infrared light irradiation and its photocatalytic mechanism. *Ind Eng Chem Res* 54(3):832–841
- Jin XC, Liu GQ, Xu ZH, Tao WY (2007) Decolorization of a dye industry effluent by *aspergillus fumigatus* XC6. *Appl Microbiol Biotechnol* 74(1):239–243
- Jo WK, Kumar S, Isaacs MA, Lee AF, Karthikeyan S (2017) Cobalt promoted TiO₂/GO for the photocatalytic degradation of oxytetracycline and Congo Red. *Appl Catal B* 201:159–168
- Kanakaraju D, Chandrasekaran A (2023) Recent advances in TiO₂/ZnS-based binary and ternary photocatalysts for the degradation of organic pollutants. *Sci Total Environ* 868:161525
- Kaur J, Singhal S (2015) Highly robust light driven ZnO catalyst for the degradation of eriochrome black T at room temperature. *Superlattices Microstruct* 83:9–21
- Keith LH, Telliard WA (1979) Priority pollutants. I. A perspective view. *Environ Sci Technol* 13(4):416–423
- Khalafi T, Buazar F, Ghanemi K (2019) Phycosynthesis and enhanced photocatalytic activity of zinc oxide nanoparticles toward organosulfur pollutants. *Sci Rep* 9(1):1–10
- Khan SH, Pathak B (2020) Zinc oxide based photocatalytic degradation of persistent pesticides: a comprehensive review. *Environ Nanotechnol Monit Manage* 13:100290
- Khan I, Saeed K, Khan I (2019) Nanoparticles: Properties, applications and toxicities. *Arab J Chem* 12(7):908–931
- Khan SR, Jamil S, Bibi S, Ali S, Habib T, Janjua MRSA (2020) A versatile material: Perovskite Bismuth Ferrite Microparticles as a potential Catalyst for enhancing fuel efficiency and degradation of various Organic Dyes. *J Inorg Organomet Polym Mater* 30(9):3761–3770
- Khataee AR, Kasiri MB (2010) Photocatalytic degradation of organic dyes in the presence of nanostructured titanium dioxide: influence of the chemical structure of dyes. *J Mol Catal A: Chem* 328(1–2):8–26
- Kolahalam LA, Viswanath IK, Diwakar BS, Govindh B, Reddy V, Murthy YLN (2019) Review on nanomaterials: synthesis and applications. *Mater Today Proc* 18:2182–2190
- Krishnan S, Rawindran H, Sinnathambi CM, Lim JW (2017) Comparison of various advanced oxidation processes used in remediation of industrial wastewater laden with recalcitrant pollutants. In: *IOP Conference Series: Materials Science and Engineering* (Vol. 206, No. 1, p 012089). IOP Publishing
- Krithiga T, Sathish S, Renita AA, Prabu D, Lokesh S, Geetha R, ..., Sillanpaa M (2022) Persistent organic pollutants in water resources: Fate, occurrence, characterization and risk analysis. *Sci Total Environ* 831:154808
- Kubiak A, Siwińska-Ciesielczyk K, Bielan Z, Zielińska-Jurek A, Jesionowski T (2019) Synthesis of highly crystalline photocatalysts based on TiO₂ and ZnO for the degradation of organic impurities under visible-light irradiation. *Adsorption* 25(3):309–325
- Kumar S, Sharma AK, Rawat SS, Jain DK, Ghosh S (2013) Use of pesticides in agriculture and livestock animals and its impact on environment of India. *Asian J Environ Sci* 8(1):51–57
- Lai MTL, Lai CW, Lee KM, Chook SW, Yang TCK, Chong SH, Juan JC (2019) Facile one-pot solvothermal method to synthesize solar active Bi₂WO₆ for photocatalytic degradation of organic dye. *J Alloys Compd* 801:502–510
- Laurent S, Forge D, Port M, Roch A, Robic C, Elst V, L., Muller RN (2010) Magnetic Iron oxide nanoparticles: synthesis, stabilization, vectorization, physicochemical characterizations, and Biological Applications. *Chem Rev* 4(110):2574–2574
- Le GH, Ngo QT, Nguyen TT, Nguyen QK, Quan TT, Vu LD, ..., Vu TA (2018) High catalytic activity of phenol photodegradation from aqueous solution with Novel Fe-Fe₃O₄-GO nanocomposite. *J Mater Eng Perform* 27(8):4225–4234
- Lee YS, Kim SJ, Venkateswaran P, Jang JS, Kim H, Kim JG (2008) Anion co-doped Titania for solar photocatalytic degradation of dyes. *Carbon Lett* 9(2):131–136
- Li Z, Sheikholeslami M, Shafee A, Haq RU, Khan I, Tlili I, Kandasamy R (2019) Solidification process through a solar energy storage enclosure using various sizes of Al₂O₃ nanoparticles. *J Mol Liq* 275:941–954
- Lipskikh OI, Korotkova EI, Khristunova YP, Berek J, Kratochvil B (2018) Sensors for voltammetric determination of food azo dyes—A critical review. *Electrochim Acta* 260:974–985

- Liu Z, Ling Q, Cai Y, Xu L, Su J, Yu K, ..., Wang X (2022) Synthesis of carbon-based nanomaterials and their application in pollution management. *Nanoscale Adv*
- Longnecker MP, Klebanoff MA, Zhou H, Brock JW (2001) Association between maternal serum concentration of the DDT metabolite DDE and preterm and small-for-gestational-age babies at birth. *The Lancet* 358(9276):110–114
- Loureiro A, Azoia G, Gomes NC, A., Cavaco-Paulo A (2016) Albumin-based nanodevices as drug carriers. *Curr Pharm Design* 22(10):1371–1390
- Lu B, Zeng S, Li C, Wang Y, Pan X, Zhang L, ..., Ye Z (2018) Nanoscale pn heterojunctions of BiOI/nitrogen-doped reduced graphene oxide as a high performance photocatalyst. *Carbon* 132:191–198
- Maktabifard M, Zaborowska E, Makinia J (2018) Achieving energy neutrality in wastewater treatment plants through energy savings and enhancing renewable energy production. *Rev Environ Sci Bio/Technol* 17:655–689
- Martis E, Badve R, Degwekar M (2012) Nanotechnology based devices and applications in medicine: an overview. *Chron Young Sci* 3(1):68–68
- Mei A, Xu Z, Wang X, Liu Y, Chen J, Fan J, Shi Q (2022) Photocatalytic materials modified with carbon quantum dots for the degradation of organic pollutants under visible light: a review. *Environ Res* 114160
- Nabi I, Ahmad F, Zhang L (2021) Application of titanium dioxide for the photocatalytic degradation of macro-and micro-plastics: a review. *J Environ Chem Eng* 9(5):105964
- Naseem T, Durrani T (2021) The role of some important metal oxide nanoparticles for wastewater and antibacterial applications: a review. *Environ Chem Ecotoxicol* 3:59–75
- Nasseri S, Omidvar Borna M, Esrafil A, Rezaei Kalantary R, Kakavandi B, Sillanpää M, Asadi A (2018) Photocatalytic degradation of malathion using Zn²⁺-doped TiO₂ nanoparticles: statistical analysis and optimization of operating parameters. *Appl Phys A* 124(2):1–11
- Nguyen AT, Hsieh CT, Juang RS (2016) Substituent effects on photo-degradation of phenols in binary mixtures by hybrid H₂O₂ and TiO₂ suspensions under UV irradiation. *J Taiwan Inst Chem Eng* 62:68–75
- Nguyen VN, Tran DT, Nguyen MT, Le TTT, Ha MN, Nguyen MV, Pham TD (2018) Enhanced photocatalytic degradation of methyl orange using ZnO/graphene oxide. *Res Chem Intermed* 44(5):3081–3095
- Ni J, Xue J, Shen J, He G, Chen H (2018) Fabrication of ZnAl mixed metal-oxides/RGO nanohybrid composites with enhanced photocatalytic activity under visible light. *Appl Surf Sci* 441:599–606
- Nikalje AP (2015) Nanotechnology and its applications in medicine. *Med chem* 5(2):081–089
- Ogugbue CJ, Sawidis T (2011) Bioremediation and detoxification of synthetic wastewater containing triarylmethane dyes by *Aeromonas hydrophila* isolated from industrial effluent. *Biotechnol Res Int*
- Ohsaka T, Shinozaki K, Tsuruta K, Hirano K (2008) Photo-electrochemical degradation of some chlorinated organic compounds on n-TiO₂ electrode. *Chemosphere* 73(8):1279–1283
- Ore OT, Adeola AO, Bayode AA, Adedipe DT, Nomngongo PN (2023) Organophosphate pesticide residues in environmental and biological matrices: occurrence, distribution and potential remedial approaches. *Environ Chem Ecotoxicol* 5:9–23
- Oyekunle JAO, Yussuf NA, Durodola SS, Adekunle AS, Adenuga AA, Ayinuola O, Ogunfowokan AO (2019) Determination of polycyclic aromatic hydrocarbons and potentially toxic metals in commonly consumed beef sausage roll products in Nigeria. *Heliyon* 5(8):e02345
- Oyekunle JAO, Adekunle AS, Adewole AM, Elugoke SE, Durodola SS, Oyeboode BA (2021) Determination of organochlorine pesticide residues in some evaporated milk samples in Nigeria using gas chromatography-mass spectrometry. *Chem Afr* 4:349–366
- Panji A, Simha LU, Nagabhushana BM (2016) Heavy metals removal by nickel-oxide nanoparticles synthesised by lemon juice extract. *Int J Eng Manag Res* 4(4):287–291
- Patel HM, Dixit BC (2014) Synthesis, characterization and dyeing assessment of novel acid azo dyes and mordent acid azo dyes based on 2-hydroxy-4-methoxybenzophenone-5-sulfonic acid on wool and silk fabrics. *J Saudi Chem Soc* 18(5):507–512
- Pattnaik A, Sahu JN, Poonia AK, Ghosh P (2023) Current perspective of nano-engineered metal oxide based photocatalysts in advanced oxidation processes for degradation of organic pollutants in wastewater. *Chem Eng Res Des* 190:667–686
- Penell J, Lind L, Salihovic S, van Bavel B, Lind PM (2014) Persistent organic pollutants are related to the change in circulating lipid levels during a 5 year follow-up. *Environ Res* 134:190–197
- Rabbani MAD, Khalili B, Saeidian H (2020) Novel edaravone-based azo dyes: efficient synthesis, characterization, antibacterial activity, DFT calculations and comprehensive investigation of the solvent effect on the absorption spectra. *RSC Adv* 10(59):35729–35739
- Ramzan H, Kausar F, Zeeshan U, Yasmeen R (2019) Strategies to Control the Pollution caused by Textile Industry Effluents containing dyes. *LGU J Life Sci* 3(3):163–174
- Rani M, Shanker U, Jassal V (2017) Recent strategies for removal and degradation of persistent & toxic organochlorine pesticides using nanoparticles: a review. *J Environ Manage* 190:208–222
- Rengarajan T, Rajendran P, Nandakumar N, Lokeshkumar B, Rajendran P, Nishigaki I (2015) Exposure to polycyclic aromatic hydrocarbons with special focus on cancer. *Asian Pac J Trop Biomed* 5(3):182–189
- Robinson T, McMullan G, Marchant R, Nigam P (2001) Remediation of dyes in textile effluent: a critical review on current treatment technologies with a proposed alternative. *Bioresour Technol* 77(3):247–255
- Rogozea EA, Petcu AR, Olteanu NL, Lazar CA, Cadar D, Mihaly M (2017) Tandem adsorption-photodegradation activity induced by light on NiO-ZnO p-n couple modified silica nanomaterials. *Mater Sci Semiconduct Process* 57:1–11
- Roos V, Rönn M, Salihovic S, Lind L, Bavel BV, Kullberg J, ..., Lind PM (2013) Circulating levels of persistent organic pollutants in relation to visceral and subcutaneous adipose tissue by abdominal MRI. *Obesity* 21(2):413–418
- Rostami M, Badiei A, Ganjali MR, Rahimi-Nasrabadi M, Naddafi M, Karimi-Maleh H (2022) Nano-architectural design of TiO₂ for high performance photocatalytic degradation of organic pollutant: a review. *Environ Res* 212:113347
- Sahu MK (2019) Semiconductor nanoparticles theory and applications. *Int J Appl Eng Res* 14(2):491–494
- Samuel O, Othman MHD, Kamaludin R, Dzinun H, Imtiaz A, Li T, ..., Kurniawan TA (2023) Photocatalytic degradation of recalcitrant aromatic hydrocarbon compounds in oilfield-produced water: a critical review. *J Clean Prod* 137567
- Scida K, Stege PW, Haby G, Messina GA, García CD (2011) Recent applications of carbon-based nanomaterials in analytical chemistry: critical review. *Anal Chim Acta* 691(1–2):6–17
- Senasu T, Nanan S (2017) Photocatalytic performance of CdS nanomaterials for photodegradation of organic azo dyes under artificial visible light and natural solar light irradiation. *J Mater Sci: Mater Electron* 28:17421–17441
- Shah M (2014) Effective treatment systems for azo dye degradation: a joint venture between physico-chemical & microbiological process. *Int J Environ Bioremediat Biodegradation* 2(5):231–242

- Silvestri S, Fajardo AR, Iglesias BA (2022) Supported porphyrins for the photocatalytic degradation of organic contaminants in water: a review. *Environ Chem Lett* 1–41
- Sivagami K, Vikraman B, Krishna RR, Swaminathan T (2016) Chlorpyrifos and Endosulfan degradation studies in an annular slurry photo reactor. *Ecotoxicol Environ Saf* 134:327–331
- Son BT, Long NV, Hang NTN (2021) The development of biomass-derived carbon-based photocatalysts for the visible-light-driven photodegradation of pollutants: a comprehensive review. *RSC Adv* 11(49):30574–30596
- Srivastava N, Mukhopadhyay M (2014) Biosynthesis of SnO₂ nanoparticles using bacterium *Erwinia herbicola* and their photocatalytic activity for degradation of dyes. *Ind Eng Chem Res* 53(36):13971–13979
- Subhiksha V, Kokilavani S, Khan SS (2022) Recent advances in degradation of organic pollutant in aqueous solutions using bismuth based photocatalysts: a review. *Chemosphere* 290:133228
- Suman S, Sinha A, Tarafdar A (2016) Polycyclic aromatic hydrocarbons (PAHs) concentration levels, pattern, source identification and soil toxicity assessment in urban traffic soil of Dhanbad, India. *Sci Total Environ* 545:353–360
- Syafrudin M, Kristanti RA, Yuniarto A, Hadibarata T, Rhee J, Al-Onazi WA, ..., Al-Mohaimed AM (2021) Pesticides in drinking water—a review. *Int J Environ Res Public Health* 18(2):468
- Tang X, Tang R, Xiong S, Zheng J, Li L, Zhou Z, ..., Liao C (2022) Application of natural minerals in photocatalytic degradation of organic pollutants: a review. *Sci Total Environ* 812:152434
- Ullah R, Dutta J (2008) Photocatalytic degradation of organic dyes with manganese-doped ZnO nanoparticles. *J Hazard Mater* 156(1–3):194–200
- Umukoro EH, Peleyeju MG, Ngila JC, Arotiba OA (2016) Photocatalytic degradation of acid blue 74 in water using Ag–Ag₂O–ZnO nanostructures anchored on graphene oxide. *Solid State Sci* 51:66–73
- Vaiano V, Sacco O, Matarangolo M (2018) Photocatalytic degradation of paracetamol under UV irradiation using TiO₂-graphite composites. *Catal Today* 315:230–236
- Veisi H, Razeghi S, Mohammadi P, Hemmati S (2019) Silver nanoparticles decorated on thiol-modified magnetite nanoparticles (Fe₃O₄/SiO₂-Pr-S-Ag) as a recyclable nanocatalyst for degradation of organic dyes. *Mater Sci Eng C* 97:624–631
- Wang Q, Yang Z (2016) Industrial water pollution, water environment treatment, and health risks in China. *Environ Pollut* 218:358–365
- Wang Z, Li Y, Cheng Q, Wang X, Wang J, Zhang G (2022) Sb-based photocatalysts for degradation of organic pollutants: a review. *J Clean Prod* 133060
- Yuan X, Zhang X, Sun L, Wei Y, Wei X (2019) Cellular toxicity and immunological effects of carbon-based nanomaterials. *Part Fibre Toxicol* 16(1):1–27
- Yun Y, Gao R, Yue H, Liu X, Li G, Sang N (2017) Polycyclic aromatic hydrocarbon (PAH)-containing soils from coal gangue stacking areas contribute to epithelial to mesenchymal transition (EMT) modulation on cancer cell metastasis. *Sci Total Environ* 580:632–640
- Zaytseva O, Neumann G (2016) Carbon nanomaterials: production, impact on plant development, agricultural and environmental applications. *Chem Biol Technol Agric* 3(1):1–26
- Zhang LH, Zhu Y, Lei BR, Li Y, Zhu W, Li Q (2018) Trichromatic dyes sensitized HKUST-1 (MOF-199) as scavenger towards reactive blue 13 via visible-light photodegradation. *Inorg Chem Commun* 94:27–33
- Zhang M, Wang J, Zhao Q, Mishra V, Fan J, Sun Y (2020) Polycyclic aromatic hydrocarbons (PAHs) and esophageal carcinoma in Handan-Xingtai district, North China: a preliminary study based on cancer risk assessment. *Environ Monit Assess* 192:1–20
- Zhao Z, Li M, Zhang L, Dai L, Xia Z (2015) Design principles for heteroatom-doped carbon nanomaterials as highly efficient catalysts for fuel cells and metal–air batteries. *Adv Mater* 27(43):6834–6840
- Zhou Y, Zhang H, Cai L, Guo J, Wang Y, Ji L, Song W (2018) Preparation and characterization of macroalgae biochar nanomaterials with highly efficient adsorption and photodegradation ability. *Materials* 11(9):1709

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Springer Nature or its licensor (e.g. a society or other partner) holds exclusive rights to this article under a publishing agreement with the author(s) or other rightsholder(s); author self-archiving of the accepted manuscript version of this article is solely governed by the terms of such publishing agreement and applicable law.

Terms and Conditions

Springer Nature journal content, brought to you courtesy of Springer Nature Customer Service Center GmbH (“Springer Nature”).

Springer Nature supports a reasonable amount of sharing of research papers by authors, subscribers and authorised users (“Users”), for small-scale personal, non-commercial use provided that all copyright, trade and service marks and other proprietary notices are maintained. By accessing, sharing, receiving or otherwise using the Springer Nature journal content you agree to these terms of use (“Terms”). For these purposes, Springer Nature considers academic use (by researchers and students) to be non-commercial.

These Terms are supplementary and will apply in addition to any applicable website terms and conditions, a relevant site licence or a personal subscription. These Terms will prevail over any conflict or ambiguity with regards to the relevant terms, a site licence or a personal subscription (to the extent of the conflict or ambiguity only). For Creative Commons-licensed articles, the terms of the Creative Commons license used will apply.

We collect and use personal data to provide access to the Springer Nature journal content. We may also use these personal data internally within ResearchGate and Springer Nature and as agreed share it, in an anonymised way, for purposes of tracking, analysis and reporting. We will not otherwise disclose your personal data outside the ResearchGate or the Springer Nature group of companies unless we have your permission as detailed in the Privacy Policy.

While Users may use the Springer Nature journal content for small scale, personal non-commercial use, it is important to note that Users may not:

1. use such content for the purpose of providing other users with access on a regular or large scale basis or as a means to circumvent access control;
2. use such content where to do so would be considered a criminal or statutory offence in any jurisdiction, or gives rise to civil liability, or is otherwise unlawful;
3. falsely or misleadingly imply or suggest endorsement, approval, sponsorship, or association unless explicitly agreed to by Springer Nature in writing;
4. use bots or other automated methods to access the content or redirect messages
5. override any security feature or exclusionary protocol; or
6. share the content in order to create substitute for Springer Nature products or services or a systematic database of Springer Nature journal content.

In line with the restriction against commercial use, Springer Nature does not permit the creation of a product or service that creates revenue, royalties, rent or income from our content or its inclusion as part of a paid for service or for other commercial gain. Springer Nature journal content cannot be used for inter-library loans and librarians may not upload Springer Nature journal content on a large scale into their, or any other, institutional repository.

These terms of use are reviewed regularly and may be amended at any time. Springer Nature is not obligated to publish any information or content on this website and may remove it or features or functionality at our sole discretion, at any time with or without notice. Springer Nature may revoke this licence to you at any time and remove access to any copies of the Springer Nature journal content which have been saved.

To the fullest extent permitted by law, Springer Nature makes no warranties, representations or guarantees to Users, either express or implied with respect to the Springer nature journal content and all parties disclaim and waive any implied warranties or warranties imposed by law, including merchantability or fitness for any particular purpose.

Please note that these rights do not automatically extend to content, data or other material published by Springer Nature that may be licensed from third parties.

If you would like to use or distribute our Springer Nature journal content to a wider audience or on a regular basis or in any other manner not expressly permitted by these Terms, please contact Springer Nature at

onlineservice@springernature.com